

# EXAFS study of glasses of the CaO–Ga<sub>2</sub>O<sub>3</sub>–GeO<sub>2</sub> system

DAMIAN CHELSTOWSKI<sup>1</sup>, AGNIESZKA WITKOWSKA<sup>1</sup>, JAROSŁAW RYBICKI<sup>1</sup>, BOHDAN PADLYAK<sup>2,\*</sup>,  
ANGELA TRAPANANTI<sup>3</sup>, EMILIANO PRINCIPI<sup>3</sup>

<sup>1</sup>Faculty of Technical Physics and Applied Mathematics, and TASK Computer Centre,  
Gdańsk University of Technology, ul. Gabriela Narutowicza 11/12, 80–952 Gdańsk, Poland.

<sup>2</sup>Department of Physics, Kazimierz Wielki Academy of Bydgoszcz, pl. Weysenhoffa 11,  
85–072 Bydgoszcz, Poland.

<sup>3</sup>INFM UdR Camerino, Dipartimento di Fisica, Università di Camerino, Via Madonna delle Carceri,  
I-62032 Camerino, MC, Italy.

X-ray absorption spectroscopy (XAS) measurements for Ca<sub>3</sub>Ga<sub>2</sub>Ge<sub>3</sub>O<sub>12</sub> and Ca<sub>3</sub>Ga<sub>2</sub>Ge<sub>4</sub>O<sub>14</sub> glasses are presented. In particular, the extended X-ray absorption fine structure (EXAFS) spectra are analysed and local neighbourhood of Ga and Ge atoms is described in detail. The Ge/Ga atoms neighbourhood in considered glasses is compared with the data available for corresponding crystals. Performed comparative crystal-glass structural analysis confirms correlation between crystalline and glassy structures of the Ca<sub>3</sub>Ga<sub>2</sub>Ge<sub>3</sub>O<sub>12</sub> and Ca<sub>3</sub>Ga<sub>2</sub>Ge<sub>4</sub>O<sub>14</sub> compounds. Our results provide several new detailed data, and some general suggestions on the CaO–Ga<sub>2</sub>O<sub>3</sub>–GeO<sub>2</sub> glass structure.

Keywords: oxide glasses, structural analysis, EXAFS.

## 1. Introduction

Disordered crystals and glass matrices doped with transition and rare-earth metals ions are still very attractive as possible laser media (especially for tunable solid state lasers) [1], [2], optical fibers [3] and for other applications in optoelectronics. In contrast to crystals, the spectroscopic properties and peculiarities due to the incorporation of transition metal ions into glasses have been studied to an insufficient extent, because the valence state and size of glass network formers, modifiers, and

---

\*On leave from Department of Physics, Ivan Franko National University of Lviv, Dragomanov Str. 50, 79–005 Lviv, Ukraine.

stabilizers change, which leads to a great variety of different local crystal fields at activator sites. Therefore, experimental investigations and theoretical analysis of spectroscopic properties of transition impurity metal ions in disordered compounds, particularly, compositionally (or substitutionally) disordered oxide crystals and glasses are current topics of solid state physics and optical materials technology. This also concerns CaO–Ga<sub>2</sub>O<sub>3</sub>–GeO<sub>2</sub> compounds, which can be obtained in crystalline and glassy (vitreous) states. These compounds are novel materials for quantum electronics and other applications. The most promising potential applications of compounds in the CaO–Ga<sub>2</sub>O<sub>3</sub>–GeO<sub>2</sub> systems are:

- tunable laser materials (also for ultrashort pulses) when doped with Cr<sup>3+</sup> and Cr<sup>4+</sup> ions;
- scintillators and radiation phosphors when doped with Ce<sup>3+</sup> ions;
- lasers for telecommunication purposes when doped with Nd<sup>3+</sup>, Ho<sup>3+</sup> and other rare-earth ions emitting in eye-safe spectral region.

In the Ca–Ga–Ge–O ternary system there exist three stable crystalline forms: Ca<sub>3</sub>Ga<sub>2</sub>Ge<sub>3</sub>O<sub>12</sub> (ordered garnet structure, space group *Ia3d*), Ca<sub>3</sub>Ga<sub>2</sub>Ge<sub>4</sub>O<sub>14</sub> (substitutionally disordered Ca-gallogermanate structure, space group *P321*), Ca<sub>2</sub>Ga<sub>2</sub>GeO<sub>7</sub> (gelenite structure, space group *P4̄2<sub>1</sub>m*) [4], [5]. Glassy forms with compositions similar to the stoichiometric crystals also exist [6]. The previous structural studies on CaO–Ga<sub>2</sub>O<sub>3</sub>–GeO<sub>2</sub> glasses by X-ray scattering and molecular dynamics methods have been presented in [7]. Comparative analysis of the X-ray data for CaO–Ga<sub>2</sub>O<sub>3</sub>–GeO<sub>2</sub> glasses and their crystalline analogs suggests that Ga/GeO<sub>6</sub> octahedra and Ga/GeO<sub>4</sub> tetrahedra form the glass network. The structure of glasses with the Ca<sub>3</sub>Ga<sub>2</sub>Ge<sub>3</sub>O<sub>12</sub>, Ca<sub>3</sub>Ga<sub>2</sub>Ge<sub>4</sub>O<sub>14</sub> and Ca<sub>3</sub>Ga<sub>2</sub>O<sub>6</sub> compositions are characterised by short-range order similar as in the corresponding crystalline compounds.

In ordered calcium-gallium-germanium garnet crystal, the Ga<sup>3+</sup> cations occupy, in general, octahedral (*a*)-sites of the lattice. Neutronography technique shows that only a small part (< 0.1 at%) of Ga<sup>3+</sup> cations occupy tetrahedral (*d*)-sites [8]. In the substitutionally disordered Ca-gallogermanate crystals the Ga<sup>3+</sup> and Ge<sup>4+</sup> cations are statistically distributed among octahedral (*1a*) and tetrahedral (*3f*)-sites of the lattice. Using X-ray data it was estimated that the average ratio Ga<sup>3+</sup>:Ge<sup>4+</sup> is equal to 1:4 for octahedral sites, and 3:2 for tetrahedral sites of the Ca-gallogermanate lattice [9]. It should be noted that the Ga<sup>3+</sup>:Ge<sup>4+</sup> ratio depends on technological conditions during the crystal growth.

At present we need a detailed structural study of glasses of the CaO–Ga<sub>2</sub>O<sub>3</sub>–GeO<sub>2</sub> system, particularly of local neighbourhoods of Ga and Ge atoms. The EXAFS method is characterised by atomic selectivity and a high sensitivity to the short-range order, and thus it appears to be the most suitable technique to study the neighbourhood of Ge and Ga atoms in multi-component and disordered systems. For these reasons we performed structural investigations for glasses with garnet (Ca<sub>3</sub>Ga<sub>2</sub>Ge<sub>3</sub>O<sub>12</sub>), and Ca-gallogermanate (Ca<sub>3</sub>Ga<sub>2</sub>Ge<sub>4</sub>O<sub>14</sub>) composition, using the X-ray absorption spectroscopy (XAS, *e.g.*, [10]), and the extended X-ray absorption fine structure analysis (EXAFS, *e.g.*, [11]).

The paper is organised as follows. Section 2 contains experimental details. In Section 3, we present and discuss the results of our measurements. Section 4 contains concluding remarks.

## 2. Experiment

In this section, we present some details on sample preparation technique (Sec. 2.1), XAS measurements (Sec. 2.2) and EXAFS data analysis (Sec. 2.3).

### 2.1. Sample preparation

The  $\text{CaO-Ga}_2\text{O}_3\text{-GeO}_2$  glasses of high optical quality and chemical purity with different compositions were obtained in corundum crucibles by high-temperature synthesis technique according to [6]. Chemical composition of the obtained glasses ( $\text{Ca}_3\text{Ga}_2\text{Ge}_3\text{O}_{12}$ ,  $\text{Ca}_3\text{Ga}_2\text{Ge}_4\text{O}_{14}$ ) was controlled by the X-ray microanalysis method using a Camebax apparatus.

Samples for the EXAFS measurements were obtained by mixing of the powdered glasses with an inert matrix powder (BN of 99% purity) in weigh ratio 1:10, and pressing the resulting mixture into pellets of a typical thickness of 0.5–1 mm, and diameter of 13 mm.

### 2.2. XAS measurements

The XAFS spectra of  $\text{Ca}_3\text{Ga}_2\text{Ge}_3\text{O}_{12}$  and  $\text{Ca}_3\text{Ga}_2\text{Ge}_4\text{O}_{14}$  glasses at the Ge and Ga  $K$ -edges have been recorded at the BM29 beam-line at the European Synchrotron Radiation Facility, Grenoble [12], using a double-crystal monochromator equipped with Si(311) crystals. An average resolution in the whole range of energy was around 1.5 eV. The room temperature measurements were performed in the energy ranges

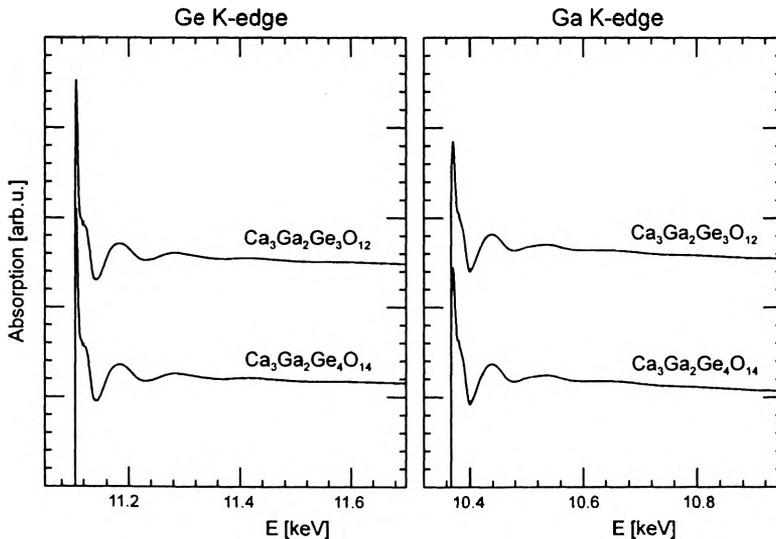


Fig. 1. XANES spectra of the considered glasses recorded at Ge and Ga  $K$ -edges.

10980–12300 eV and 10250–11100 eV for Ge and Ga *K*-edges, respectively (the Ge *K*-edge energy amounts to 11104 eV, and Ga *K*-edge to 10367 eV). Obtained XAFS spectra of the glasses are presented in Fig. 1.

### 2.3. EXAFS data analysis

Experimental data have been analysed with an advanced technique, using theoretical calculations of the X-ray absorption cross-section in the framework of the GNXAS method (GN – refers to the *n*-body distribution function in condensed matter, XAS – as above, for details see [13]–[15]). The method is based on the comparison in the energy space between the experimental signal,  $\alpha_{\text{exp}}(E)$ , and the theoretical one,  $\alpha_{\text{mod}}(E)$ , attempting to optimise the relevant structural ( $R$ ,  $\sigma^2$ ,  $\beta$ ,  $N$ ), and related non-structural ( $S_0^2$ ,  $E_0$ ) parameter values. The meaning of the structural parameters mentioned above is as follows. Parameter  $R$  is the mean inter-atomic distance,  $\sigma^2$  is the Debye–Waller-like parameter, describing both the structural and vibrational disorder,  $\beta$  is the skewness parameter, and  $N$  is the co-ordination number. The non-structural parameter  $S_0^2$ , *i.e.*, the amplitude reduction factor, takes into account inelastic processes. Finally, the  $E_0$  parameter gives the difference between experimental and theoretical energy scales. In our GNXAS analysis the theoretical signal was modelled taking into account the following three-shell frequency contributions: Ge–O, Ge–Ca and Ge–Ga for Ge-edge spectra, and Ga–O, Ga–Ca and Ga–Ge for Ga-edge spectra. In addition, the GNXAS method has shown a high flexibility in the modelling of the atomic backgrounds due to the possibility of accounting for multi-electron excitation channels. In our analysis the ( $1s_{1/2}3d$ ), ( $1s_{1/2}3p$ ) and ( $1s_{1/2}3s$ ) channels have been considered.

## 3. Results and discussion

The results of the fitting procedure are shown in Figs. 2 and 3. The obtained structural parameters are presented in Tabs. 1 and 2.

Preliminary structural investigations (X-ray diffraction and molecular dynamics simulations [7]) of the CaO–Ga<sub>2</sub>O<sub>3</sub>–GeO<sub>2</sub> glasses show that the structure is characterised by short-range chemical ordering similar to ordering of the corresponding crystalline compounds [4], [5], [9]. For this reason the comparative crystal-glass structural analysis was performed. Let us describe in turn the structure around Ge and Ga atoms in Ca<sub>3</sub>Ga<sub>2</sub>Ge<sub>3</sub>O<sub>12</sub> (Sec. 3.1) and Ca<sub>3</sub>Ga<sub>2</sub>Ge<sub>4</sub>O<sub>14</sub> (Sec. 3.2) glasses.

### 3.1. Structure of the Ca<sub>3</sub>Ga<sub>2</sub>Ge<sub>3</sub>O<sub>12</sub> glass

As it is seen from Fig. 2 and Tab. 1, for Ca<sub>3</sub>Ga<sub>2</sub>Ge<sub>3</sub>O<sub>12</sub> glass, in the Ge-related subsystem, similarly as in the corresponding crystal, regular GeO<sub>4</sub> units are present ( $N \approx 4.0$  and small value of  $\sigma^2$  and  $\beta$  parameters). Disorder parameters of Ge–Ca/Ga correlations also assume similar values as in the ordered garnet structure.

The Ga-related subsystem structure, in the nearest neighbourhood of Ge atoms, is characterised by two types of structural units: GaO<sub>4</sub> (Ga–O<sub>1</sub> correlation) and GaO<sub>6</sub>

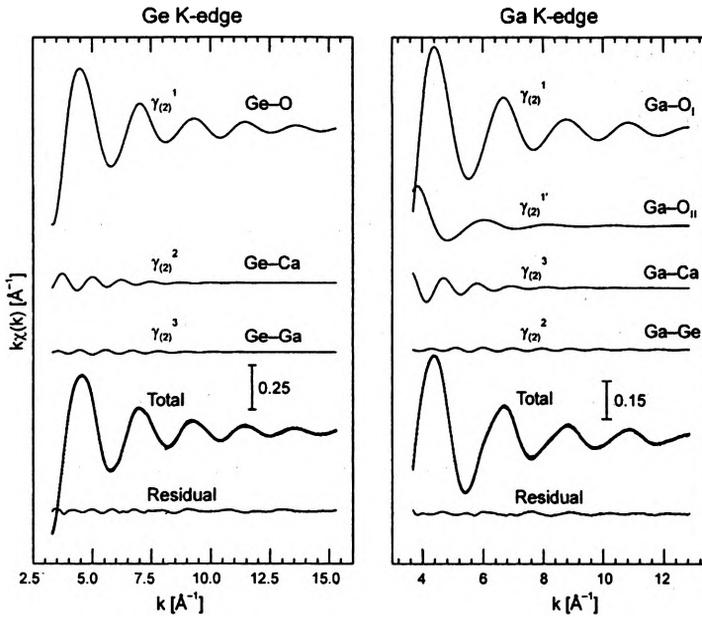


Fig. 2. Results of the GNXAS analysis performed for spectra recorded at Ge and Ga-edges of  $\text{Ca}_3\text{Ga}_2\text{Ge}_3\text{O}_{12}$  glass (solid line – model; dotted – experiment). See also Tab. 1.

Table 1. Structural parameters of  $\text{Ca}_3\text{Ga}_2\text{Ge}_3\text{O}_{12}$  glass derived from Ge and Ga K-edges EXAFS analysis. The symbols are explained in the text.

$\text{Ca}_3\text{Ga}_2\text{Ge}_3\text{O}_{12}$	$R$ [Å]	$\sigma^2$ [Å <sup>2</sup> ]	$\beta$	$N$
Ge–O	1.75	0.002	0.47	3.90
Ge–Ca	3.14	0.030	0.78	2.40
Ge–Ga	3.42	0.048	0.80	4.00
Ga–O <sub>I</sub>	1.87	0.004	1.32	3.81
Ga–O <sub>II</sub>	2.29	0.095	1.20	6.00
Ga–Ca	3.51	0.062	0.81	5.90
Ga–Ge	3.97	0.104	1.24	4.19

(Ga–O<sub>II</sub> correlation). The GaO<sub>4</sub> units dominate, and are more regular than the GaO<sub>6</sub> groups (*cf.*  $\sigma^2$  parameter values). In the  $\text{Ca}_3\text{Ga}_2\text{Ge}_3\text{O}_{12}$  garnet crystal, in general, the GaO<sub>6</sub> octahedra are present, and the average Ga–O distance in crystal is smaller by  $\sim 0.2$  Å than  $R_{\text{Ga-O}}$  in the GaO<sub>6</sub> units in glass. As was noted above, in the  $\text{Ca}_3\text{Ga}_2\text{Ge}_3\text{O}_{12}$  crystals only a small ( $< 0.1$  at%) fraction of GaO<sub>4</sub> tetrahedral groups was detected by neutron diffraction technique [8].

The Ga–Ca two-body spatial correlation, in respect to disorder parameters, is similar as in the corresponding crystal. On the other hand, the Ga–Ge correlation is very irregular (high dispersion,  $\sigma^2 > 0.1$  Å<sup>2</sup>), and is also somewhat different in glass and crystal ( $\Delta R \approx 0.55$  Å,  $\Delta N \approx 2.0$ ).

The results of the structural analysis of  $\text{Ca}_3\text{Ga}_2\text{Ge}_3\text{O}_{12}$  glass suggest that while the parameters describing the Ge atom neighbourhood in glass have similar values as in the corresponding crystal, the parameters describing the Ga atom neighbourhood in glass and crystal are significantly different. One has to remember that the two-body correlations alone are insufficient to describe the shape of the basic structural units. Unfortunately, in the case of glasses, the three-body correlations are very difficult to extract. Thus, the exact shape of the dominant structural unit in the considered glasses cannot be determined univocally from the EXAFS experiment. Several forms of the basic units are compatible with our results. These might be:

- regular tetrahedra (similarly as in other glasses containing  $\text{Ga}_2\text{O}_3$ , *e.g.*, [16], [17]);
- square pyramids with oxygen atoms forming the base, and Ga atom in the vertex,
- $\text{GaO}_6$  octahedra, strongly defective due to the presence of vacancies and/or the appearance of elongated Ga–O bonds, characteristic of ordered  $\text{Ca}_3\text{Ga}_2\text{Ge}_3\text{O}_{12}$  garnet crystal; this latter hypothesis is compatible with very high structural unit irregularity found for the  $\text{GaO}_6$  groups.

### 3.2. Structure of the $\text{Ca}_3\text{Ga}_2\text{Ge}_4\text{O}_{14}$ glass

As it is seen from Fig. 3 and Tab. 2, in Ge-related subsystem, like in the corresponding crystal, both  $\text{GeO}_4$  (Ga– $\text{O}_I$  correlation) and  $\text{GeO}_6$  (Ga– $\text{O}_{II}$  correlation) units appear. In the glass the  $\text{GeO}_4$  units dominate, and are more regular than the  $\text{GeO}_6$  groups (*cf.*  $\sigma^2$  parameters). The  $R_{\text{Ge-O}}$  distances in  $\text{GeO}_4$  units in crystal and glass are very

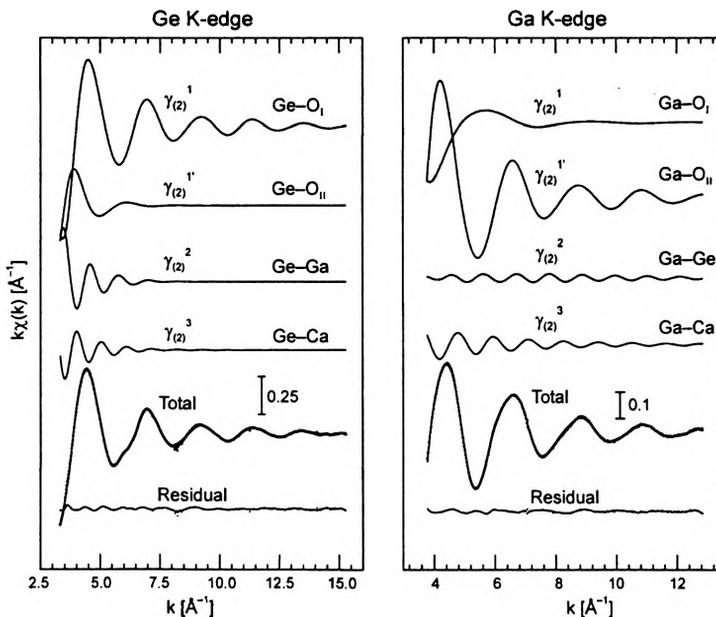


Figure 3. Results of the GNXAS analysis performed for spectra recorded at Ge and Ga-edges of  $\text{Ca}_3\text{Ga}_2\text{Ge}_4\text{O}_{14}$  glass (solid line – model; dotted – experiment). See also Tab. 2

Table 2. Structural parameters of  $\text{Ca}_3\text{Ga}_2\text{Ge}_4\text{O}_{14}$  glass derived from Ge and Ga *K*-edges EXAFS analysis. The symbols are explained in the text.

$\text{Ca}_3\text{Ga}_2\text{Ge}_4\text{O}_{14}$	$R$ [Å]	$\sigma^2$ [Å <sup>2</sup> ]	$\beta$	$N$
Ge–O <sub>I</sub>	1.77	0.002	1.14	4.00
Ge–O <sub>II</sub>	2.04	0.039	0.32	6.00
Ge–Ca	3.69	0.055	1.11	3.01
Ge–Ga	3.72	0.057	0.75	6.13
Ga–O <sub>I</sub>	1.74	0.079	1.20	4.08
Ga–O <sub>II</sub>	1.91	0.013	1.79	6.05
Ga–Ca	3.61	0.192	1.74	5.71
Ga–Ge	3.55	0.114	1.76	2.99

similar. On the other hand, this distance in  $\text{GeO}_6$  units in crystal and glass differ by about 0.1 Å. Ge–Ga/Ca distances reveal rather high dispersion (see  $\sigma^2$  and  $\beta$  parameters).

In Ga-related subsystem both  $\text{GaO}_4$  (Ga–O<sub>I</sub> correlation) and  $\text{GaO}_6$  (Ga–O<sub>II</sub> correlation) units have been detected, similarly as in substitutionally disordered Ca-gallogermanate crystal. The structural units in the glass are more compact than in the crystal ( $R_{\text{glass}} < R_{\text{crystal}}$ , and the  $\beta$  parameter obtained for glass is relatively high). In the glass the  $\text{GaO}_6$  units dominate, and are more regular than the  $\text{GaO}_4$  groups. Other two spatial correlations (Ga–Ge and Ga–Ca) are highly dispersed (very high values of  $\sigma^2$  and  $\beta$  parameters).

The results of the structural analysis of  $\text{Ca}_3\text{Ga}_2\text{Ge}_4\text{O}_{14}$  glass show that the structure around Ge and Ga atoms is characterised by short-range chemical order similar as in the corresponding crystalline compound (substitutionally disordered Ca-gallogermanate crystal). Only one difference exists:  $\text{GaO}_n$  units in the glass are more compact (the same situation was observed, *e.g.*, for  $\text{BiO}_5$  units present in bismuth-silicate glasses [18]).

## 4. Conclusions

The described results confirm that EXAFS is an efficient probe to investigate the short-range (up to third coordination shell) structure in complex oxide glasses. EXAFS experiment can distinguish between Ge/ $\text{GaO}_n$  local environments with various  $n$ .

The obtained results confirm also the correlation between crystalline and glassy structures of the considered compounds in the  $\text{CaO-Ga}_2\text{O}_3\text{-GeO}_2$  system. They provide several new detailed data, and also some general suggestions on the glass structure. However, the above preliminary results should be verified using other, independent experimental methods, like solid-state <sup>71</sup>Ga magic angle spinning nuclear magnetic resonance.

*Acknowledgments* – We would like to thank the ESRF Laboratory (Grenoble, France) for the beamtime and the BM29 staff. The work has been partially supported by grant BW/2002 of the Kazimierz Wielki Academy of Bydgoszcz, Poland.

## References

- [1] DRUBE J., STRUBE B., HUBER G., *Opt. Commun.* **50** (1984), 45.
- [2] KENYON P., ANDREWS L., MC COLLUM B., LEMPICKI A., *IEEE Quantum Electron.* **18** (1982), 1189.
- [3] YEH D.C., SIBLEY W.A., SUSCAVAGE M., DREXHANGE M.G., *J. Appl. Phys.* **62** (1987), 266.
- [4] DAMEN J.P.M., PISTORIUS J.A., ROBERTSON J.M., *Matre. Res. Bull.* **12** (1977), 73.
- [5] MILL B.V., BUTASHIN A.V., ELLERN A.M., MAJER A.A., *Izv. Akad. Nauk SSSR, Ser. Neorgan. Mater.* **17** (1981), 1648 (in Russian).
- [6] PADLYAK B.V., BUCHYNSKII P.P., Patent of Ukraine, No. UA 25235 A, 1998.
- [7] PADLYAK B.V., MUDRY S., HALCHAK V., KOROLYSHYN A., RYBICKI J., WITKOWSKA A., *Opt. Appl.* **30** (2000), 691.
- [8] NOSENKO A.E., PADLYAK B.V., *Mol. Phys. Rep.* **8** (1994), 79.
- [9] MILL B.V., BUTASHIN A.V. AND ELLERN A.M., *Izv. Akad. Nauk SSSR, Ser. Neorgan. Mater.* **19** (1983), 1715 (in Russian).
- [10] KONINGSBERGER D.C., PRINS R. [Eds.], *X-ray Absorption – Principles, Applications, Techniques of EXAFS, SEXAFS and XANES*, Wiley, New York 1988.
- [11] FILIPPONI A., DI CICCIO A., *Phys. Rev. B* **51** (1995), 12322.
- [12] <http://www.esrf.fr>
- [13] FILIPPONI A., DI CICCIO A., NATOLI C.R., *Phys. Rev. B* **52** (1995), 15122.
- [14] *Ibidem*, p. 15135.
- [15] FILIPPONI A., DI CICCIO A., *TASK Quart.* **4** (2000), 575.
- [16] MIYAJI F., YOKO T., JIN J., SAKKA S., FUKUNAGA T., MISAWA M., *J. Non-Cryst. Solids* **175** (1994), 211.
- [17] CHOI Y.G., KIM K.H., CHERNOV V.A., HEO J., *J. Non-Cryst. Solids* **259** (1999), 205.
- [18] WITKOWSKA A., RYBICKI J., MURAWSKI L., DI CICCIO A., *Mol. Phys. Rep.* **36** (2002), 133.

*Received September 26, 2002*